

**Alternative wood products from
blue-stained mountain pine beetle lumber:
non-structural laminated products**

I. Zaturecky and I. Chiu

Mountain Pine Beetle Initiative
Working Paper 2005–7

Natural Resources Canada, Canadian Forest Service,
Pacific Forestry Centre 506 West Burnside Road, Victoria, BC V8Z 1M5
(250) 363-0600 • www.pfc.cfs.nrcan.gc.ca



Natural Resources
Canada

Ressources naturelles
Canada

Canada

Canada



Alternative wood products from
blue-stained mountain pine beetle lumber:
non-structural laminated products

I. Zaturecky and I. Chiu

Mountain Pine Beetle Initiative
Working Paper 2005–7

**Natural Resources Canada
Canadian Forest Service
Pacific Forestry Centre
506 West Burnside Road
Victoria, British Columbia V8Z 1M5
Canada**

2005

Abstract

This study evaluated the potential of blue-stained lodgepole pine wood to be used for nonstructural appearance-grade laminated panels. Two methods of processing—edge gluing and face lamination—were studied. Both faces of each panel were graded for amount of stain and appearance, and recovery numbers were recorded during the process to complete the evaluation.

Of the edge-glued panels, those with a natural streak appearance were most appealing. The uniform stripe design and the alternating stripe design were least appealing. The edge-gluing method was more conducive to the manipulation of panel appearance, thereby allowing a greater recovery of the non-stained portion of production than was the face lamination method. Of the face-laminated panels, those with marbled design were most appealing. This method could not produce the natural streak design and also has limited capabilities in sorting the non-stained portion of the wood.

Key words: mountain pine beetle, *Dendroctonus ponderosae*, blue stain, wood processing, laminates, panelling, lodgepole pine, *Pinus contorta*, wood products, edge gluing, face lamination, market appeal

Résumé

La présente étude évalue la possibilité d'utiliser du bois de pin tordu latifolié bleui pour fabriquer des panneaux de finition lamellés à usage non structurel. Deux procédés de fabrication par encollage – de chant et de face – ont été évalués. Les deux faces de chaque panneau ont été classifiées d'après la quantité de bleuissement et l'aspect; le taux de récupération associé à chaque procédé a également été pris en compte aux fins de l'évaluation.

Parmi les panneaux produits par encollage du chant, ceux qui montraient un aspect strié naturel présentaient le plus grand attrait commercial. Les panneaux à motifs de rayures uniformes et de rayures alternantes présentaient le plus faible attrait commercial. En comparaison de l'encollage de face, l'encollage du chant s'est mieux prêté au travail de l'aspect des panneaux et a ainsi permis une récupération plus efficace des parties non bleuies. Parmi les panneaux obtenus par encollage de face, ceux qui montraient un aspect marbré présentaient le plus grand attrait commercial. Toutefois, cette méthode n'a pas permis de produire des panneaux présentant un aspect strié naturel, et elle a ses limites pour ce qui est du tri des parties non bleuies.

Mots clés : dendroctone du pin ponderosa, *Dendroctonus ponderosae*, bleuissement, transformation du bois, panneaux lamellés, mise en panneau, pin tordu latifolié, *Pinus contorta*, produits ligneux, encollage du chant, encollage de face, attrait commercial

Table of Contents

| | |
|--|-----------|
| Introduction | 1 |
| Methods and results | 2 |
| Manufacturing of edge-glued panels | 2 |
| Manufacturing of face-laminated panels..... | 4 |
| Assessing attractiveness of blue-stain patterns on panels..... | 6 |
| Discussion | 7 |
| Edge-glued panels | 7 |
| Face-glued panels | 10 |
| Conclusions | 10 |
| Acknowledgements | 11 |
| References | 11 |
| Contact | 11 |
| Appendix: Description of patterns | 12 |

Introduction

Infestation of lodgepole pine by mountain pine beetle in British Columbia is increasing dramatically. From 2001 to 2002, the volume of beetle attacked wood increased from 72 million cubic meters to 108 million cubic meters. The British Columbia Ministry of Forests assumes that 50% of mature pine (older than 80 years) will be killed. To date, approximately 9 million hectares of lodgepole pine stands in the central interior of the province has been dead for 1 to 2 years (red-attacked). Stands that have been dead for 3 to 4 years are classified as grey-attacked. The shelf life of killed mountain pine beetle wood is estimated to be 15 years. Consequently, the Ministry of Forests has increased annual allowable cuts in beetle-infested timber supply areas for the next 15 years. Even with this conservative estimate of affected mature pine and the increase in annual allowable cuts, there will be about 200 million cubic meters of dead standing pine after 15 years (Petersen 2004).

The two major markets for British Columbia's spruce–pine–fir lumber (SPF) are the North American dimensional lumber market and the Japanese 2 x 4-in. construction lumber market. The Japanese Agricultural Standards- (JAS-) grade lumber specified for the Japanese 2 x 4-in. construction does not permit stain. Although the current grades for the North American housing market allow some stained lumber, an increase in quantity of blue-stained pine in the mix may encounter consumer resistance.

Some efforts have been made to promote the uniqueness of blue stain for appearance-type products. A small group of manufacturers and locals around Quesnel, British Columbia, have been promoting blue-stained wood under the name, "Denim Pine". The idea behind these efforts is to convince consumers that blue stain adds character to wood and to finished products such as furniture, cabinets, flooring, panelling or shelving (<http://www.denimpine.ca>).

In this study, we evaluated the acceptability of more uniformly stained wood products for non-structural laminated products. Our specific target was to use lumber with varying degrees of blue stain and cut at a dimensional sawmill to manufacture panel or shelving products by using various laminating techniques. Panel appearance was assessed for attractiveness and potential applications.

Methods and results

Manufacturing of edge-glued panels

One package of 2.13-metre-long (84-in.) 38 mm x 89 mm (nominal 2 x 4 in) stud-grade lumber was used. Lumber was pulled out after the planer, based on the presence of at least 50% blue stain on one face. Moisture content was measured, and the lumber was stickered and air dried to 12% to 14% moisture content. The lumber was ripped to a target size of 20 mm thickness, producing strips that were 20 mm x 38 mm in size. The strips were sorted into three grades, based on amount and location of blue stain. Grade One had no stain on the piece, Grade Two contained stain on one face, and Grade Three consisted of stain on two faces. (Grade outturn is shown in Table 1.) Pieces with two-sided stain were sorted again for appearance, and put together into sets prior to edge gluing.

Table 1. Grade Outturn

| Grade: | | # Pieces | % |
|--------|--------------|----------|-------|
| 1 | No Stain | 42 | 3.7% |
| 2 | Single Stain | 40 | 3.6% |
| 3 | Double Stain | 1 044 | 92.7% |
| | Total | 1 126 | 100% |

Edge-glued panels were produced with Dural's PVA adhesive G2539, using a hot press made by Kallesoe. Pressing parameters included a platen temperature of 90°C, and a press time of 20 minutes using a press-specific pressure of 828 kPa (120psi).

Using a total of nine strips, the edge-glued panels were 314 mm (12 3/8") wide. Several different designs were produced by mixing and matching pieces together. A total of 68 edge-glued panels were produced. Each panel was visually graded for amount of blue stain and appearance. The amount of stain ranged from 0% to 95%. Terms used to describe blue-stain patterns on the panels are as follows: no stain, uniform, very uniform, uniform stripe, alternating stripes, random, random marbled, random scattered, random blotched, few scattered, and natural streaks.

Both faces of each panel were graded for amount of stain and appearance. The amount of stain on each face of a given panel was visually estimated. After visually assessing the amount of blue stain on a face, the face was evaluated for appearance.

Table 2 shows the amount of stain and appearance of the edge-glued panels. The first column contains the code which identifies the panel. For example, 59a refers to Side A of panel 59 and 59b refers to Side B of panel 59. The second column contains information on amount of stain in terms of percentage. Appearance of the face is described in the third column. Terms used to describe the blue-stain patterns are defined in Appendix 1.

Table 2. Edge-glued panels

| Code | %Stain | Appearance |
|------|--------|--------------------------|
| 59a | 0 | no stain |
| 59b | 0 | no stain |
| 58a | 0 | no stain |
| 58b | 0 | no stain |
| 57a | 0 | no stain |
| 57b | 0 | no stain |
| 60a | 0 | no stain |
| 60b | 0 | no stain |
| 53a | 20 | uniform stripe |
| 53b | 30 | uniform stripe |
| 54a | 95 | uniform |
| 54b | 90 | uniform |
| 49a | 15 | uniform stripe |
| 49b | 20 | uniform stripe |
| 50a | 45 | very uniform |
| 50b | 45 | very uniform |
| 51a | 40 | marbled random |
| 51b | 35 | random |
| 41a | 25 | uniform stripe |
| 41b | 20 | uniform stripe |
| 42a | 40 | alternating solid stripe |
| 42b | 40 | alternating solid stripe |
| 48a | 10 | random scattered |
| 48b | 15 | random scattered |
| 30a | 30 | uniform stripe |
| 30b | 30 | uniform stripe |
| 40a | 75 | uniform |
| 40b | 65 | uniform |
| 39a | 5 | few scattered |
| 39b | 5 | few scattered |
| 36a | 50 | random |
| 36b | 50 | marbled random |
| 35a | 10 | random |
| 35b | 10 | random |
| 33a | 35 | uniform stripe |
| 33b | 30 | uniform stripe |
| 25a | 40 | random |
| 25b | 50 | random |
| 32a | 25 | random |
| 32b | 25 | random |
| 31a | 25 | random |
| 31b | 25 | random |
| 23a | 35 | uniform stripe |

| Code | %Stain | Appearance |
|------|--------|-----------------|
| 23b | 40 | uniform stripe |
| 22a | 85 | uniform |
| 22b | 80 | uniform |
| 24a | 25 | uniform stripe |
| 24b | 25 | uniform stripe |
| 20a | 40 | natural streaks |
| 20b | 40 | random streaks |
| 14a | 40 | natural streaks |
| 14b | 40 | natural streaks |
| 18a | 40 | uniform stripe |
| 18b | 30 | uniform stripe |
| 19a | 90 | uniform |
| 19b | 80 | uniform |
| 16a | 80 | uniform |
| 16b | 70 | uniform |
| 15a | 25 | uniform stripe |
| 15b | 30 | marbled random |
| 4a | 30 | random |
| 4b | 30 | random |
| 5a | 95 | uniform |
| 5b | 90 | uniform |
| 6a | 50 | random |
| 6b | 55 | random |
| 68a | 0 | ns |
| 68b | 0 | ns |
| 67a | 0 | ns |
| 67b | 0 | ns |
| 66a | 0 | ns |
| 66b | 0 | ns |
| 65a | 5 | random |
| 65b | 10 | random |
| 63a | 0 | ns |
| 63b | 0 | ns |
| 64a | 5 | random |
| 64b | 0 | ns |
| 62a | 15 | random blotched |
| 62b | 0 | ns |
| 61a | 0 | ns |
| 61b | 0 | ns |
| 52a | 90 | uniform |
| 52b | 75 | uniform |
| 56a | 25 | random |
| 56b | 20 | random |
| 55a | 30 | uniform stripe |

| Code | %Stain | Appearance |
|------|--------|---------------------|
| 55b | 30 | uniform stripe |
| 47a | 75 | natural streaks |
| 47b | 50 | random |
| 46a | 60 | natural streaks |
| 46b | 60 | natural streaks |
| 45a | 60 | random marbled |
| 45b | 60 | random marbled |
| 43a | 75 | random |
| 43b | 75 | random |
| 44a | 10 | random |
| 44b | 15 | random |
| 37a | 35 | random |
| 37b | 35 | random |
| 34a | 25 | random |
| 34b | 30 | random |
| 29a | 50 | uniform stripe |
| 29b | 65 | uniform stripe |
| 38a | 60 | alternating stripes |
| 38b | 50 | uniform stripe |
| 27a | 50 | uniform stripe |
| 27b | 50 | uniform stripe |
| 28a | 40 | alternating stripes |
| 28b | 50 | alternating stripes |
| 26a | 50 | marbled |
| 26b | 30 | random |

| Code | %Stain | Appearance |
|------|--------|----------------|
| 21a | 40 | uniform stripe |
| 21b | 40 | uniform stripe |
| 17a | 25 | random |
| 17b | 35 | random |
| 13a | 40 | uniform stripe |
| 13b | 40 | uniform stripe |
| 12a | 25 | uniform stripe |
| 12b | 25 | uniform stripe |
| 10a | 40 | uniform stripe |
| 10b | 40 | uniform stripe |
| 9a | 90 | uniform |
| 9b | 75 | uniform |
| 11a | 15 | random |
| 11b | 15 | random |
| 7a | 25 | random |
| 7b | 25 | random |
| 8a | 40 | uniform stripe |
| 8b | 40 | uniform stripe |
| 3a | 15 | random |
| 3b | 15 | random |
| 2a | 40 | uniform stripe |
| 2b | 40 | uniform stripe |
| 1a | 50 | marbled |
| 1b | 40 | marbled |

Manufacturing of face-laminated panels

A second package of 2.13-metr-long (84-in.) 38 mm x 89 mm (nominal 2 x 4 in.) stud-grade lumber was used. The same grade of lumber as used in the previous section was selected, re-dried to 12% to 14% moisture content and processed. Lumber was planed to a thickness of 35 mm and the width of 86 mm. After planing, the lumber was sorted into two grades: Grade One consisted of lumber with blue stain on one face; Grade Two had blue stain on both faces.

Before face gluing, pieces were sorted again, based on amount and pattern of blue stain.

The blue-stained lumber was pre-sorted into blocks before glue application. Laminated blocks with dimensions 89 mm x 305 mm x 2.13 m (3.5 in. x 12 in. x 84 in.) were produced with PVA adhesive from Dural G2539, using a Kallesoe hydraulic hot press. Pressing parameters included a platen temperature of 90°C, and a press time of 20 minutes with a press-specific pressure of 828 kPa (120 psi).

A total of 20 blocks were made. Three panels, each measuring 25.4 mm (1") thick, were sawn from each block. The panels were graded visually for amount and appearance of stain on both faces, using the same methodology as was used to grade the edge-glued panel set. (See Table 3 for details on amount of stain and visual appearance of each board.)

Table 3. Face-laminated panels

| Sample | % Stain | Appearance |
|--------|---------|----------------------|
| 1-1a | 95 | uniform |
| 1-1b | 60 | random stripes |
| 1-2a | 55 | random stripes |
| 1-2b | 5 | scattered few |
| 1-3a | 5 | scattered few |
| 1-3b | 0 | no stain |
| 2-1a | 70 | alternating stripes |
| 2-1b | 15 | random scattered |
| 2-2a | 15 | random scattered |
| 2-2b | 5 | few stripes |
| 2-3a | 5 | few stripes |
| 2-3b | 5 | few stripes |
| 3-1a | 100 | uniform |
| 3-1b | 60 | blotched |
| 3-2a | 60 | blotched |
| 3-2b | 15 | few stripes |
| 3-3a | 15 | few stripes |
| 3-3b | 0 | no stain |
| 4-1a | 40 | alternating stripes |
| 4-1b | 20 | alternating stripes |
| 4-2a | 20 | alternating stripes |
| 4-2b | 10 | scattered stripes |
| 4-3a | 10 | scattered stripes |
| 4-3b | 5 | few stripes one side |
| 5-1a | 70 | gradient |
| 5-1b | 40 | random |
| 5-2a | 40 | random |
| 5-2b | 10 | scattered |
| 5-3a | 10 | scattered |
| 5-3b | 15 | uneven |
| 8-1a | 70 | uniform |
| 8-1b | 40 | mixed stripes |
| 8-2a | 40 | mixed stripes |
| 8-2b | 20 | mixed stripes |
| 8-3a | 20 | mixed stripes |
| 8-3b | 30 | mixed stripes |
| 6-1a | 95 | marbled |

| Sample | % Stain | Appearance |
|--------|---------|----------------|
| 6-1b | 80 | marbled |
| 6-2a | 80 | marbled |
| 6-2b | 15 | few stripes |
| 6-3a | 15 | few stripes |
| 6-3b | 5 | few stripes |
| 7-1a | 50 | uniform stripe |
| 7-1b | 30 | uniform stripe |
| 7-2a | 30 | uniform stripe |
| 7-2b | 30 | uniform stripe |
| 7-3a | 30 | uniform stripe |
| 7-3b | 40 | uniform stripe |
| 11-1a | 65 | uniform stripe |
| 11-1b | 20 | uniform stripe |
| 11-2a | 20 | uniform stripe |
| 11-2b | 35 | uniform stripe |
| 11-3a | 35 | uniform stripe |
| 11-3b | 60 | uniform stripe |
| 10-1a | 35 | marbled |
| 10-1b | 25 | uniform stripe |
| 10-2a | 25 | uniform stripe |
| 10-2b | 30 | uniform stripe |
| 10-3a | 30 | uniform stripe |
| 10-3b | 70 | marbled |
| 9-1a | 95 | uniform |
| 9-1b | 80 | uniform |
| 9-2a | 80 | uniform |
| 9-2b | 50 | uniform |
| 9-3a | 50 | uniform |
| 9-3b | 65 | uniform |
| 14-1a | 95 | uniform |
| 14-1b | 50 | uniform |
| 14-2a | 50 | uniform |
| 14-2b | 35 | random |
| 14-3a | 35 | random |
| 14-3b | 25 | random |
| 13-1a | 90 | uniform |
| 13-1b | 50 | uniform |
| 13-2a | 50 | uniform |

| Sample | % Stain | Appearance |
|--------|---------|----------------|
| 13-2b | 40 | uniform |
| 13-3a | 40 | uniform |
| 13-3b | 40 | uniform |
| 12-1a | 85 | uniform |
| 12-1b | 40 | uniform |
| 12-2a | 40 | uniform |
| 12-2b | 30 | uniform |
| 12-3a | 30 | uniform |
| 12-3b | 40 | uniform |
| 17-1a | 50 | uniform |
| 17-1b | 35 | uniform |
| 17-2a | 35 | uniform |
| 17-2b | 50 | uniform |
| 17-3a | 50 | uniform |
| 17-3b | 75 | uniform |
| 16-1a | 30 | uniform |
| 16-1b | 20 | uniform |
| 16-2a | 20 | uniform |
| 16-2b | 20 | uniform |
| 16-3a | 20 | uniform |
| 16-3b | 30 | uniform |
| 15-1a | 50 | uniform stripe |
| 15-1b | 30 | uniform stripe |

| Sample | % Stain | Appearance |
|--------|---------|-----------------|
| 15-2a | 30 | uniform stripe |
| 15-2b | 30 | uniform stripe |
| 15-3a | 30 | uniform stripe |
| 15-3b | 40 | random stripes |
| 19-1a | 80 | marbled |
| 19-1b | 65 | marbled |
| 19-2a | 65 | marbled |
| 19-2b | 50 | marbled |
| 19-3a | 50 | marbled |
| 19-3b | 50 | marbled |
| 18-1a | 95 | uniform |
| 18-1b | 80 | uniform |
| 18-2a | 80 | uniform |
| 18-2b | 70 | uniform |
| 18-3a | 70 | uniform |
| 18-3b | 80 | uniform |
| 20-1a | 40 | uniform stripes |
| 20-1b | 15 | random stripes |
| 20-2a | 15 | random stripes |
| 20-2b | 25 | random stripes |
| 20-3a | 25 | random stripes |
| 20-3b | 30 | random stripes |


Assessing attractiveness of blue-stain patterns on panels

Attractiveness, or visual appeal, of different patterns produced from the edge-glued and laminated blue-stained pine lumber was assessed according to the ability of the lay-up to resemble the natural look of custom-cut boards from the same type of log. Custom cutting of logs uses a cutting pattern that differs from that used in dimensional sawmills, and produces natural-looking, mostly flat-grain boards. This is a preferable method to produce furniture components or stock in which appearance is a factor. The most desirable patterns in edge-glued and face-laminated panels looked very natural, with glue lines completely hidden: it was similar in appearance to boards cut from mountain pine beetle-killed logs. The least desirable pattern looked artificial, with glue lines clearly visible: the panels differed greatly in appearance from boards cut from mountain pine beetle-killed logs.

Discussion

Summarized data for all panels was graphed and is shown in Figure 1.

Figure 1. Summarized panel data

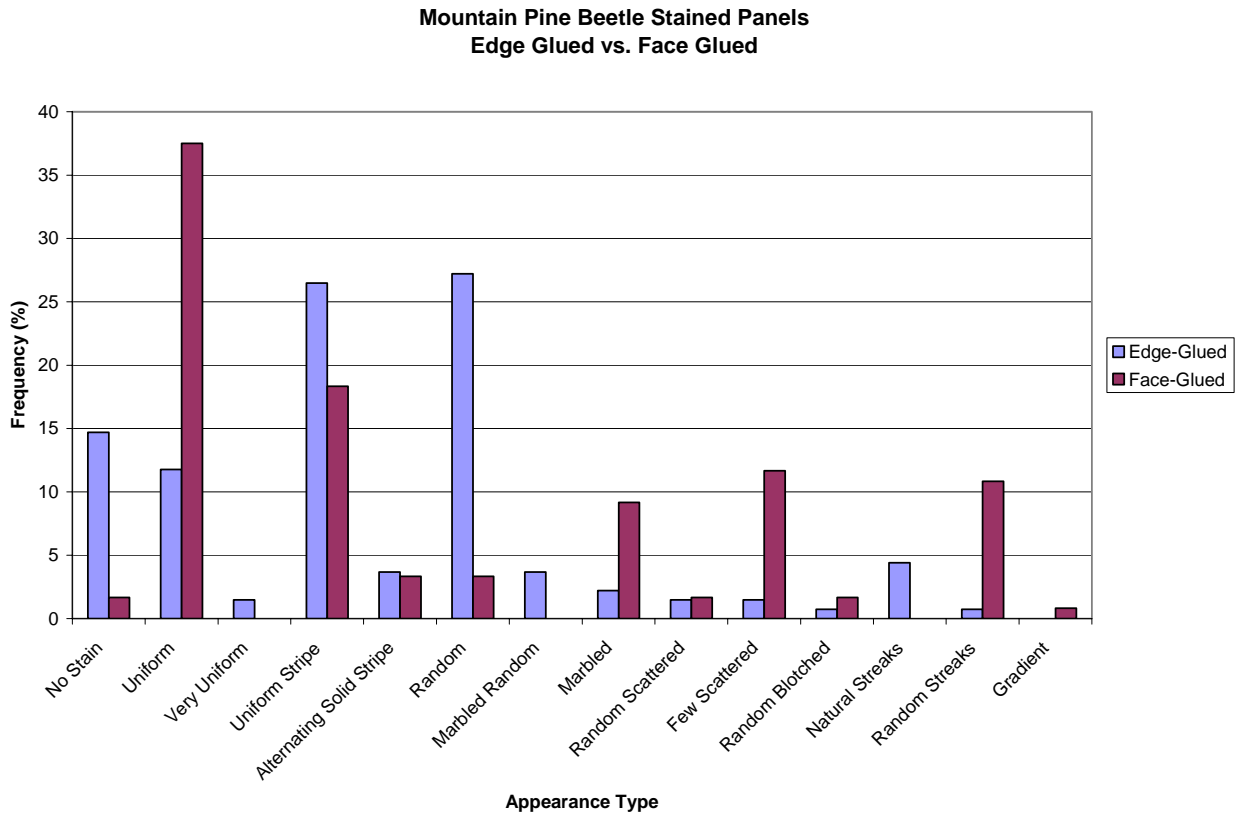

Edge-glued panels

Panels made with a natural streak design (Figure 2) were the most desirable. The glue lines between the strips were hidden within the blue stain; this produces a natural-looking design. It also compares to boards sawn specifically for appearance for flooring or panelling. These results indicate that lumber from dimensional sawmill can be successfully used for value-added products and compete against custom-cut lumber.

Figure 2. Left: 50% natural streak; right: 40% natural streak



The uniform stripe (Figure 3) and alternating stripe design (Figure 4) were least desirable in appearance compared to the natural streak design.

Figure 3. Left: 40% uniform stripe; right: 25% uniform stripe



Figure 4. Left: 60% alternating stripe; Right: 50% alternating stripe



Panels made with uniform (Figure 5), random (Figure 5), and marbled designs were more visually appealing than were the uniform and alternating stripe designs, but less appealing than was the natural streak design.

Figure 5. Left: 90% Uniform; Right: 25% Random



Face-glued panels

For the face-laminated samples in this set, no panels were produced with a natural streak pattern. The most desirable panel produced in this set had a marbled design; however, occurrence of this pattern was low, and would not be commercially viable to produce. Panels with the alternating stripe design were the least visually appealing.

The face-gluing method has limited potential for sorting, grading and pre-selection of patterns before gluing. One advantage may be higher productivity compared to that of an edge-gluing process when blue-stain pattern is not critical.

Conclusions

There is greater control over panels' final appearance by re-sawing stained mountain pine beetle dimensional lumber into strips and then edge gluing them than by face gluing lumber into blocks and re-sawing them into panels.

The two most visually appealing blue stain patterns were natural streak and marbled. Both patterns resembled boards custom cut for flooring or panelling, and had an advantage of dimensional stability provided by narrow strips. Uniform and uniform stripe patterns were somewhat desirable patterns. The least visually appealing were panels with the alternating stripe pattern.

It should be noted that beauty is in the eye of beholder, and the ultimate decision on appeal of appearance of a certain pattern will lie with the customer. A marketing study is recommended to gauge market preferences.

Acknowledgements

This project is funded by the Government of Canada through the Mountain Pine Beetle Initiative, a six-year, \$40 million program administered by Natural Resources Canada, Canadian Forest Service. Publication does not necessarily signify that the contents of this report reflect the views or policies of Natural Resources Canada, Canadian Forest Service.

The authors would like to thank Mr. Mel Weikum and Mr. Dean Doyle, of Canfor Clear Lake division. In addition we would like to thank Mr. Frank Lam of UBC Faculty of Forestry and his team of graduate students for their work on other parts of this project, data compilation and report writing.

References

Petersen, L. 2004. Mountain pine beetle epidemic in BC: from a timber supply perspective [online]. BC Ministry of Forests, Forest Practices Branch. Presentation to UBC on Feb 12, 2004. Available from http://www.for.gov.bc.ca/hfp/mountain_pine_beetle/symposium/cf.pdf. [Viewed 4 March, 2004]

Project contact

Frank Lam. 2424 Main Mall, Vancouver, BC. V6T 1Z4. franklam@interchange.ubc.ca

Appendix: Description of patterns

No stain: no trace of blue stain in the wood

Uniform: stain is equally distributed along the length and width

Very Uniform: stain is equally distributed along the length and width more than uniform

Uniform stripe: stain covers an area about half in width on each lamina along the full length

Alternating solid stripe: stained pieces are mixed with unstained pieces alternating

Random: no determined pattern

Marbled random: marbled lamina with no determined pattern

Marbled: has the look of marble

Random scattered: lamina contains small amounts of blue stain that are arranged with no determined pattern

Few scattered: lamina with sparsely streaks of stain not more than 5 inches in length

Random blotched: stain resembles spots of paint thrown about without order

Natural streaks: stain is oriented so that the glue lines are not noticed

Random streaks: stain is oblong in shape and spread about without order


Gradient: stain in lamina from 0% to 100% stain from one edge to the other edge

This publication is funded by the Government of Canada through the Mountain Pine Beetle Initiative, a program administered by Natural Resources Canada, Canadian Forest Service (web site: mpb.cfs.nrcan.gc.ca).

Contact:

For more information on the Canadian Forest Service, visit our web site at:
www.nrcan.gc.ca/cfs-scf

or contact the Pacific Forestry Centre
506 West Burnside Road
Victoria, BC V8Z 1M5
Tel: (250) 363-0600 Fax: (250) 363-0775
www.pfc.cfs.nrcan.gc.ca

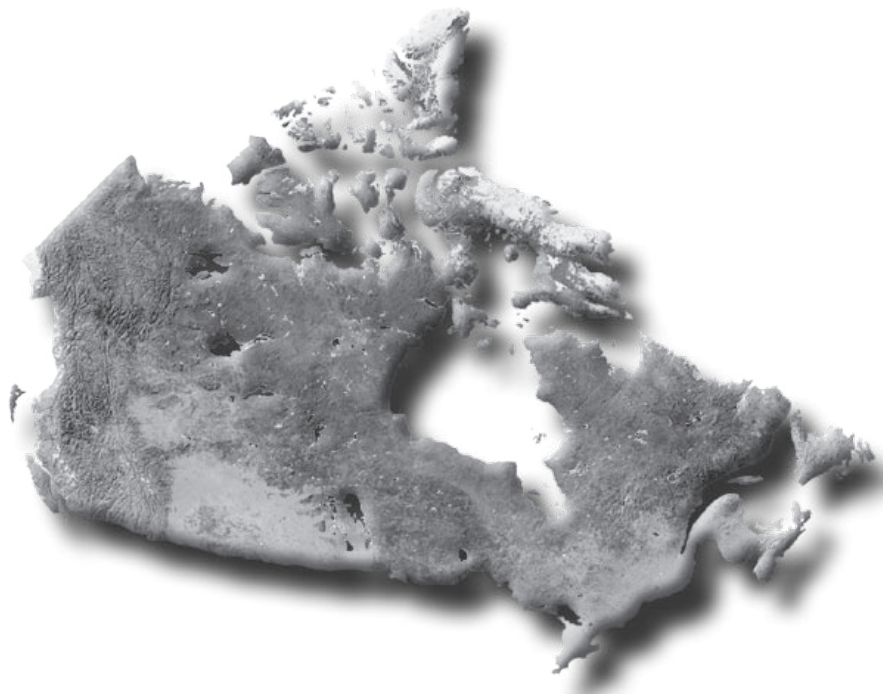

To order publications on-line, visit the Canadian Forest Service Bookstore at:
bookstore.cfs.nrcan.gc.ca